

Full Length Article

Magnetic properties of ϵ iron(III) oxide nanorod arrays functionalized with gold and copper(II) oxide



Chiara Maccato^a, Giorgio Carraro^{a,*}, Davide Peddis^b, Gaspare Varvaro^{b,*},
Davide Barreca^c

^a Department of Chemistry, Padova University and INSTM, 35131 Padova, Italy

^b CNR-ISM, Monterotondo Scalo, 00015 Roma, Italy

^c CNR-ICMATE and INSTM, Department of Chemistry, Padova University, 35131 Padova, Italy

ARTICLE INFO

Article history:

Received 27 June 2017

Received in revised form 29 August 2017

Accepted 4 September 2017

Available online 6 September 2017

Keywords:

Epsilon iron oxide

Gold

Copper

Magnetic properties

ABSTRACT

A sequential Chemical Vapor Deposition (CVD) – Radio Frequency (RF)-sputtering approach was adopted to fabricate supported nanocomposites based on the scarcely investigated ϵ -iron(III) oxide polymorph. In particular, ϵ -Fe₂O₃ nanorod arrays were obtained by CVD, and their subsequent functionalization with Au and CuO nanoparticles (NPs) was carried out by RF-sputtering under mild operational conditions. Beside a multi-technique characterization of material structure, morphology and chemical composition, particular efforts were dedicated to the investigation of their magnetic properties. The pertaining experimental data, discussed in relation to the system chemico-physical characteristics, are directly dependent on the actual chemical composition, as well as on the spatial distribution of Au and CuO nanoparticles. The approach adopted herein can be further implemented to control and tailor different morphologies and phase compositions of iron oxide-based nanomaterials, meeting thus the open requests of a variety of technological utilizations.

© 2017 Elsevier B.V. All rights reserved.

1. Introduction

Nanomaterials based on iron(III) oxides, eventually functionalized with metal or metal oxide nanoparticles (NPs), are attractive platforms for various technological applications, encompassing biomedicine, (photo)catalysis, solar assisted H₂ generation, gas sensing/batteries, and magnetic devices [1–7]. To this regard, due to the search for iron oxide-based nanomaterials endowed with specific features, the scarcely investigated ϵ -Fe₂O₃ polymorph has emerged for its peculiar properties with respect to the most stable and widely studied γ -Fe₂O₃ and α -Fe₂O₃ [8–12]. Indeed, ϵ -Fe₂O₃ nanomaterials display a superior activity in solar-assisted photocatalytic processes [2,3,13,14] and intriguing magnetic properties, such as giant room-temperature coercive field, that can be exploited for the fabrication of electric/magnetic field or multiple-state memory devices [1,15–18]. In this context, a considerable attention has been devoted to the possibility of boosting material performances by suitable surface functionalization, that represents a strategic option for the development of multi-functional systems to be exploited in various technological applications [4]. In particu-

lar, various routes have been developed, such as grafting or coating with organic molecules, polymers, and biomolecules, or functionalization with inorganic species [1,3,4,9,16,17]. Indeed, a precise engineering of the resulting interfaces can not only exert a protective action over the underlying Fe₂O₃, but also result in the birth of improved and/or unprecedented chemical, physical and functional characteristics [3,13,14,16,19].

In this framework, the functionalization of magnetic iron oxide systems with Au NPs yields various advantages, including the stabilization of magnetic Fe₂O₃ under corrosive biological conditions. In addition, the controlled introduction of well dispersed Au nanoparticles affords magnetic systems endowed with plasmonic properties, rendering ϵ -Fe₂O₃-Au composites important candidates for various end uses, such as magnetic, photocatalytic, optical and biomedical applications [14,20–24]. Equally and otherwise interesting is the functionalization of magnetic iron oxide nanosystems with CuO NPs. CuO, an antiferromagnetic *p*-type semiconductor ($E_G \approx 1.2$ eV) with a Néel temperature of 230 K [25,26], has a broad perspective of applications as active component in superconductors and electrode materials, as well as in field emitters, solar cells, and photocatalysts [27–30]. As a matter of fact, ϵ -Fe₂O₃-CuO composites represent attractive multifunctional materials with tuneable magnetic properties [25,31,32].

In order to meet the open scientific and technological demands, the availability of versatile fabrication and processing techniques,

* Corresponding authors.

E-mail addresses: giorgio.carraro@unipd.it (G. Carraro), gaspare.varvaro@ism.cnr.it (G. Varvaro).

enabling material preparation under controlled conditions onto suitable substrates, is highly demanded [1,8,10,16,23,33–35], especially for ϵ -Fe₂O₃-Au and ϵ -Fe₂O₃-CuO materials. In fact, the synthesis of supported single phase ϵ -Fe₂O₃ nanosystems is still a challenging issue. Recently, our group has developed a CVD process for the selective preparation of ϵ -Fe₂O₃ nanosystems with tailored nano-organization [15,36]. In the present study, we report on the preparation of ϵ -Fe₂O₃-Au and ϵ -Fe₂O₃-CuO nanocomposites through a two-step preparative approach. The proposed route consists in the initial CVD of supported ϵ -Fe₂O₃ nanorod arrays, followed by the subsequent deposition of Au or CuO NPs by radio frequency (RF)-sputtering at low temperatures and applied powers, to avoid detrimental alterations of the pristine iron oxide matrix [14,32,37]. After a multi-technique characterization aimed at assessing structural, morphological, and compositional properties, the magnetic behavior of the obtained composites was investigated and discussed, with particular focus on the role of Au and CuO nanoparticles. To the best of our knowledge, no previous reports on the magnetic properties of the target materials are available in the literature up to date.

2. Experimental

2.1. Synthesis

A cold-wall CVD horizontal equipment was adopted for the preparation of iron(III) oxide nanorod arrays, using Fe(hfa)₂TMEDA (hfa = 1,1,1,5,5,5-hexafluoro-2,4-pentanedionate; TMEDA = N,N,N',N'-tetramethylethylenediamine) as a molecular source (vaporization temperature = 60 °C) [38]. Precursor vapors were delivered by an O₂ flow (purity = 6.0; rate = 100 sccm) into the reaction chamber through connection gas lines maintained at 120 °C in order to prevent detrimental condensation processes. An additional oxygen flow (100 sccm), passing through a water reservoir heated at 50 °C, was independently introduced into the CVD reactor. Depositions were performed on pre-cleaned 1 × 1 cm² Si(100) substrates (MEMC[®], Merano, Italy), using the following experimental settings: substrate temperature = 400 °C; total pressure = 10.0 mbar; deposition time = 60 min. The CVD conditions have been selected basing on our previous studies [36], in order to obtain single phase ϵ -Fe₂O₃ nanosystems.

Subsequently, as-prepared iron oxide samples were mounted into a two-electrode reaction system [39] for RF-sputtering ($\nu = 13.56$ MHz), that was conducted using pure Ar as plasma source. In particular, RF-sputter deposition of gold was performed using an Au metal target (BAL-TEC AG, 99.99%) under the following conditions: substrate temperature = 60 °C; RF-power = 5 W; total operating pressure = 0.3 mbar; Ar flow rate = 10 sccm; duration = 40 min. RF-sputter deposition of copper(II) oxide was carried out using a copper target (Alfa Aesar[®]; purity = 99.95%) under the same conditions adopted for gold, apart from the process duration (90 min). The adopted parameters were optimized in a series of preliminary experiments in order to control the overall Au (CuO) content and prevent a complete coverage of the underlying iron oxide matrices, as well as the occurrence of undesired alterations.

2.2. Characterization

X-ray Diffraction (XRD) measurements were carried out on a Dymax-RAPID X-ray microdiffractometer using Cu K α radiation.

Field Emission-Scanning Electron Microscopy (FE-SEM) measurements were carried out at primary beam acceleration voltages comprised between 10 and 20 kV by means of a Zeiss SUPRA 40VP instrument.

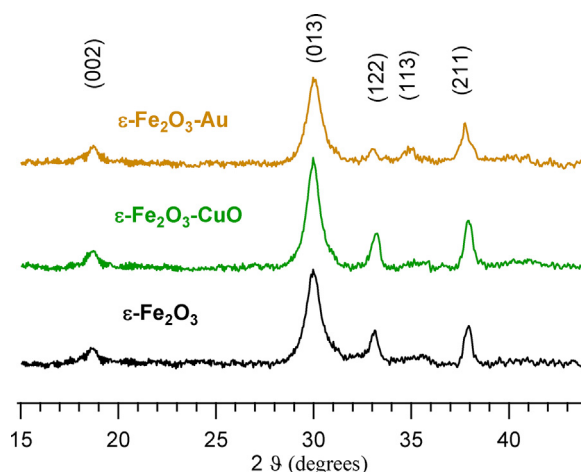


Fig. 1. XRD patterns for specimens deposited on Si(100) substrates. The pattern related to bare ϵ -Fe₂O₃ is also displayed for comparison.

X-ray Photoelectron Spectroscopy (XPS) analyses were performed by a Perkin Elmer Φ 5600ci spectrometer with a standard Al K α source (1486.6 eV), at a working pressure lower than 10⁻⁸ mbar. The reported Binding Energy (BE) values were corrected for charging effects by assigning a BE of 284.8 eV to the adventitious C1 s peak, as previously reported [40,41]. After a Shirley-type background subtraction [42], atomic percentages (at.%) were evaluated using sensitivity factor values provided by Φ V5.4 A software. The Cu Auger (α) parameter was calculated by using the following equation:

$$\alpha_{\text{Cu}} = \text{BE}(\text{Cu}2p_{3/2}) + \text{KE}(\text{CuLMM}) \quad (1)$$

with KE = kinetic energy [40,41]. The Auger parameter was used as a finger-print to unambiguously identify copper oxidation state, since it is independent on any static charging and can be measured with a higher accuracy than the core level BE or Auger peaks. In fact, since the chemical shifts of photoelectrons and Auger electrons are different, the difference between their energies constitutes a special spectral property, and its numerical value is unique for each chemical state [43,44]. The comparison of Auger parameter values with the reference ones tabulated in specialized handbooks or databases enables thus to identify the element oxidation states with high accuracy [40,41,45].

Au/Cu molar fractions were defined as [32]:

$$X_{\text{M}} = (\text{Mat.}\%)/[(\text{Mat.}\%) + (\text{Feat.}\%)] \quad (2)$$

Room temperature magnetic properties were carefully investigated by combining quasi-static field- and angle-dependent magnetization and remanent measurements performed using a vibrating sample magnetometer (model 10-MicroSense, $H_{\text{max}} = 20$ kOe). In particular, besides field-dependent magnetization loops measured along the direction parallel and perpendicular to the rod axis, advanced measurement protocols were used to investigate the magnetic interaction and the reversal mechanism.

3. Results and discussion

In the present work, the main attention was initially devoted to investigating the structure, morphology and composition of ϵ -Fe₂O₃-Au and ϵ -Fe₂O₃-CuO nanosystems, with particular regard to the system composition and distribution of Cu- and Au-containing NPs.

Fig. 1 shows the XRD patterns of the target systems, revealing the formation of ϵ -Fe₂O₃ as the only iron(III) oxide polymorph. In particular, the peaks located at $2\theta = 18.7^\circ$, 30.1° , 33.1° , 34.8° ,

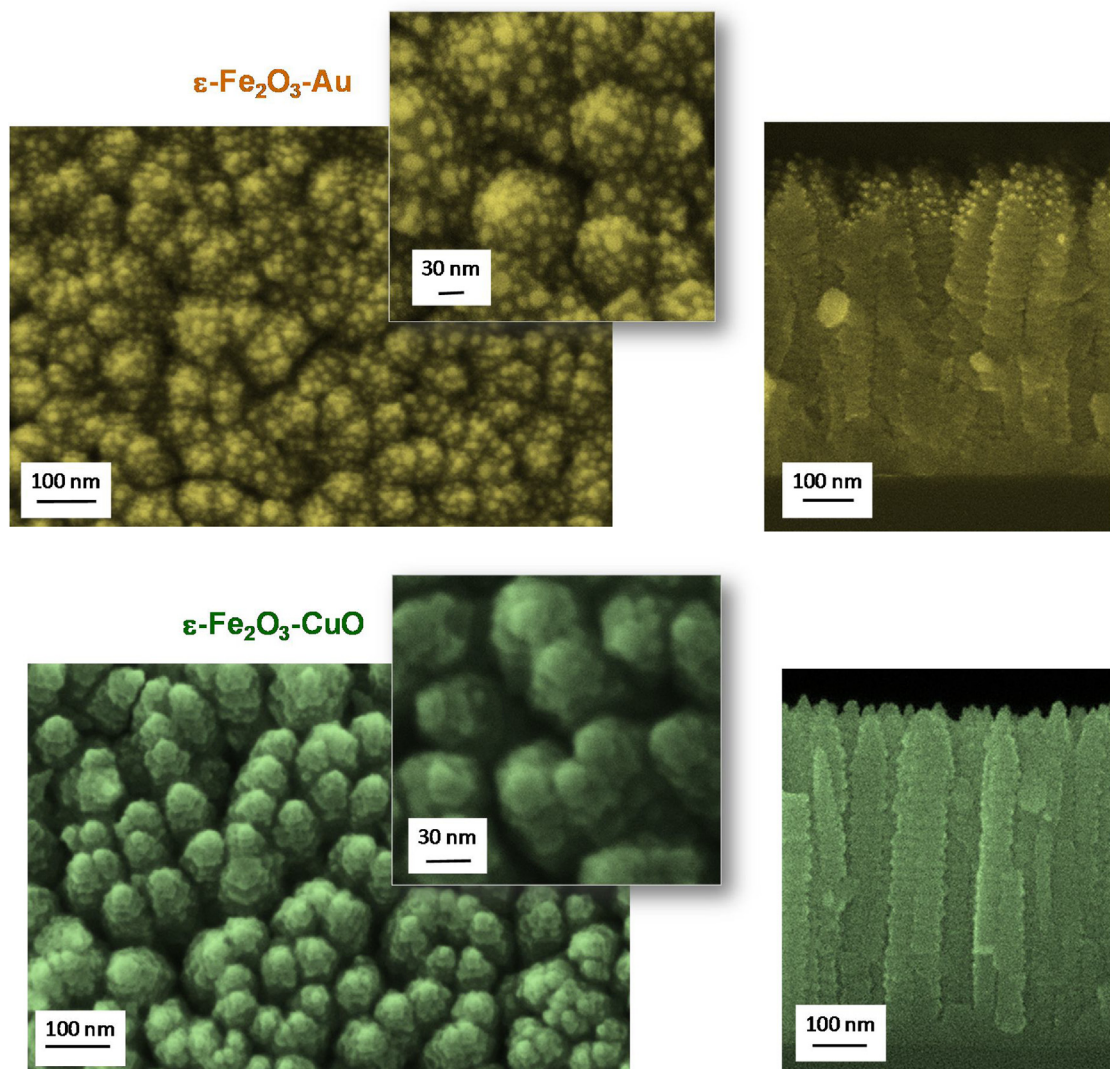


Fig. 2. Schematic view of ϵ - Fe_2O_3 crystallographic structure oriented along the [013] direction with respect to the substrate surface. The magneto-crystalline easy-axis ($\equiv a$ axis) lies in the substrate plane (i.e., along the normal to the rod axis). Atom color codes: Fe = blue; O = white.

and 37.8° could be assigned respectively to the (002), (013), (122), (113) and (211) reflections of orthorhombic ϵ - Fe_2O_3 [46] as the sole iron(III) oxide polymorph. As already discussed in our previous works [2,36], a key role for the selective obtainment of ϵ - Fe_2O_3 nanomaterials is the introduction of water vapor into the reaction atmosphere, significantly affecting the overall process. In fact, water introduction results in a diffusion-controlled process, promoting the formation of ϵ - Fe_2O_3 deposits [36] endowed with oxygen defects, that play a key role in the growth and stabilization of the metastable ϵ - Fe_2O_3 phase [2]. In a different way, in the presence of dry O_2 , a surface-reaction-limited CVD regime occurs, leading to the formation of β - Fe_2O_3 systems.

A comparison of the relative peak intensities with the reference powder spectrum suggested the occurrence of a preferential [013] orientation (see also below and Fig. 2) [36]. No significant microstructural variations occurred upon functionalization with Au or CuO NPs, due to the high dispersion and low amount of the latter species. This observation, in line with previous reports [14,32], was also confirmed by the data obtained through other characterization techniques (see below).

The morphological organization was investigated by FE-SEM analyses, highlighting the presence of porous nanorod arrays, aligned perpendicularly with respect to the Si(100) substrate

surface, with mean lateral size and length of (60 ± 10) nm and (520 ± 20) nm, respectively (Fig. 3). Both the pseudo-conic tips and the spiral-like rod shape suggested the occurrence of a spiral dislocation growth mechanism, promoted by the system tendency to decrease the total free energy [32,36,47]. The anisotropic growth responsible for the formation of these pillar-like structures was in agreement with the preferential [013] orientation evidenced by XRD analyses.

Upon functionalization with Au (or CuO) NPs, the iron oxide morphology was almost preserved thanks to the use of mild sputter deposition conditions. In Fe_2O_3 -Au composites, Au nanoparticles with an average size of (15 ± 3) nm could be clearly detected on the iron oxide tips, suggesting a three-dimensional (Volmer–Weber) growth mode, as already reported for Au deposition on oxide supports [37,48]. Upon CuO sputter deposition, a careful inspection of higher magnification images in Fig. 3 showed that nanometer-sized CuO NPs were deposited both on the tips of ϵ - Fe_2O_3 nanorods and along the entire wire walls, thanks to the porosity of the obtained arrays. This different distribution could be traced back to a higher chemical affinity of CuO NPs and ϵ - Fe_2O_3 with respect to the case of metallic gold NPs. Indeed, this difference was considered as the main responsible for the higher in-depth penetration of CuO nanoparticles [14,32].

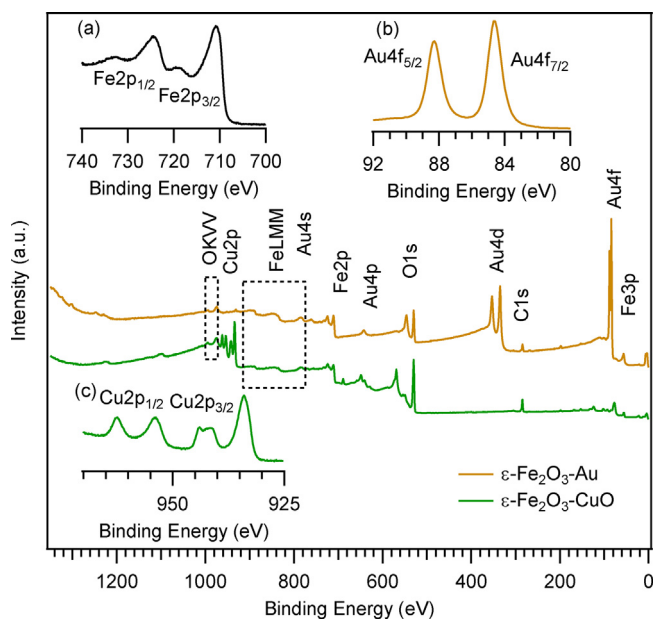


Fig. 3. Representative plane-view and cross-sectional FE-SEM images for ϵ -Fe₂O₃-based nanocomposites.

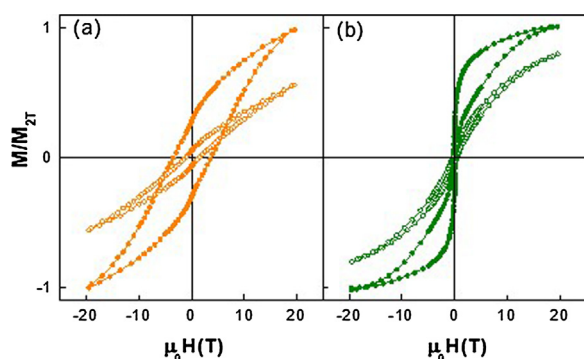


Fig. 4. Surface wide-scan XPS spectra for ϵ -Fe₂O₃ composite specimens. The corresponding (a) Fe2p, (b) Au4f and (c) Cu2p photoelectron signals are displayed as insets.

The system chemical composition was investigated by XPS analyses. Fig. 4 compares XPS wide-scan spectra for ϵ -Fe₂O₃-CuO and ϵ -Fe₂O₃-Au nanosystems, that were dominated by iron and oxygen peaks, along with a minor carbon signal (<10 at.%) due to adventitious contamination [41]. The presence of iron(III) oxide free from other Fe oxidation states was confirmed by the Fe2p signal [BE(Fe2p_{3/2}) = 711.1 eV; spin-orbit splitting = 13.7 eV, Fig. 4 a]. The O1s signal (not shown) resulted from the contribution of lattice oxygen in Fe₂O₃ (and also in CuO for the ϵ -Fe₂O₃-CuO sample; BE = 530.0 eV) and surface -OH species (BE = 531.8 eV) [15,36,41,45]. Accordingly, the O/Fe atomic ratio was slightly higher than the expected stoichiometric value. For the ϵ -Fe₂O₃-Au sample, Au photoelectron peaks were well evident, and the Au4f_{7/2} BE (84.5 eV) confirmed the presence of metallic gold NPs (Fig. 4 b) [28,41,45]. As a matter of fact, this BE value resulted to be ≈ 0.4 eV higher than the typical ones reported for metallic gold, a phenomenon related to both charge exchange and relaxation/screening phenomena [14,48]. Regarding the ϵ -Fe₂O₃-CuO specimens, the formation of Cu(II) oxide was evidenced by: i) the Cu2p peak position [Fig. 4c; BE(Cu2p_{3/2}) = 934.1 eV]; ii) the presence of shake-up satellites at BE ≈ 9.0 eV higher than the principal spin-orbit components; iii) the value of the Auger param-

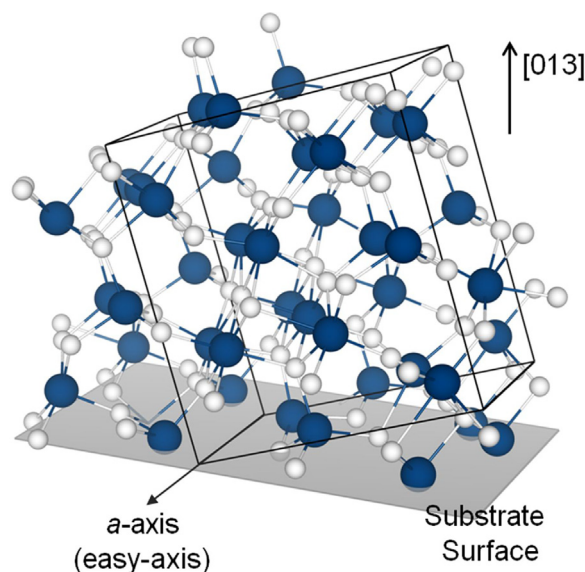


Fig. 5. Room temperature field-dependent magnetization loops for samples: (a) ϵ -Fe₂O₃-Au, and (b) ϵ -Fe₂O₃-CuO, recorded with the external magnetic field applied either parallel (open circles) or perpendicular (closed circles) to the rod axis.

eter ($\alpha_{\text{Cu}} = 1851.5$ eV) [30,32,41,45]. Calculations of molar fractions yielded similar values for Au and Cu ($X_{\text{Au}} = 0.5$; $X_{\text{Cu}} = 0.6$).

A preliminary investigation of NP effects on the magnetic behavior of ϵ -Fe₂O₃ rods was performed by recording at 300 K the field-dependent magnetization loops along the directions parallel and perpendicular to the rod axis (Fig. 5). The larger hysteresis observed along the perpendicular direction indicated that the magnetization preferentially aligns along the normal to the rod axis, which represents the direction of minimum energy, i.e. the magnetic easy-axis. To explain the observed magnetic anisotropy symmetry, the two main contributions to the effective anisotropy were taken into account: the magneto-crystalline anisotropy (K_{mc}), closely related to the material structure and symmetry, and the shape anisotropy (K_{sh}), that would favour the magnetization alignment along the rod axis. The large magneto-crystalline anisotropy of the ϵ -Fe₂O₃ phase ($K_{\text{mc}} \approx 0.2 - 0.5 \text{ MJ} \times \text{m}^{-3}$) [18] significantly overcomes the shape anisotropy arising from the elongated rod shape, being the upper limit for a uniformly magnetized and infinite wire equal to $K_{\text{sh}} = 1/2 \mu_0 M_s^2 \approx 3.5 - 10 \text{ kJ} \times \text{m}^{-3}$ (where $M_s \approx 75 - 125 \text{ kA/m}$ is the saturation magnetization [18]). On this basis, it can be suggested that the magneto-crystalline anisotropy represents the main contribution for the presently investigated systems. The preferential [013] rod orientation, as detected by XRD analysis, indicates that the *a*-axis of the ϵ -Fe₂O₃ orthorhombic cell corresponding to the magnetic easy-axis associated to the magnetocrystalline anisotropy [16,49], is mainly directed along the normal to the rod axis (Fig. 2), explaining thus the observed anisotropy symmetry. In addition, also the dipolar interaction among the rods could contribute to the development of a magnetic easy-axis perpendicular to the rod axis itself [50]. It is worthwhile noticing that, along the easy-axis direction, both the samples do not reach a saturation state even under an external applied field of ≈ 2 T. This phenomenon was related to the lack of ferrimagnetic order and/or to the relative low value of the maximum available field, insufficient to reach saturation due to the high ϵ -Fe₂O₃ magneto-crystalline anisotropy [15]. Although the magnetic phase was the same in both the samples, ϵ -Fe₂O₃-Au exhibited a nearly single-phase behavior, whereas ϵ -Fe₂O₃-CuO showed a constricted hysteresis loop along the normal to the rod axis, which indicated the co-existence of two magnetic phases with different anisotropy. Since bare ϵ -Fe₂O₃ rods showed a single-phase behavior [15], such

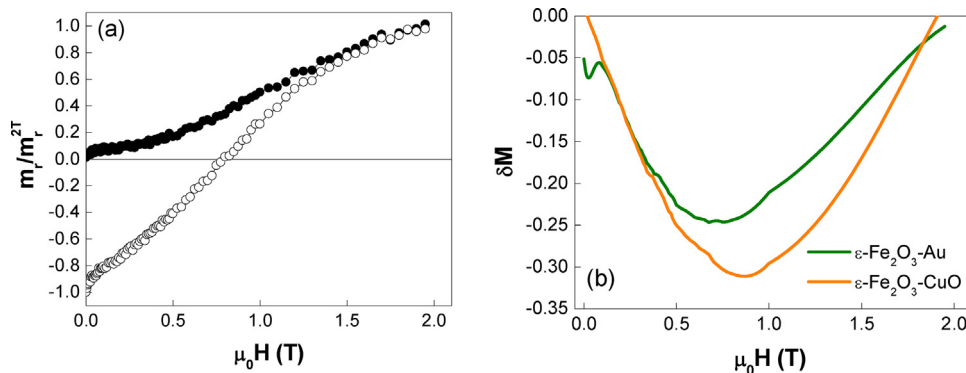


Fig. 6. (a) Comparison between the IRM (closed circles) and DCD (open circles) remanence curves for the ε -Fe₂O₃-Au sample; the curves are normalized to the remanent moment measured after applying an external field of 2 T (m_r/m_r^{2T}). (b) δM plots derived from the remanence curves.

a result suggested that the nanoparticle decoration played a key role in determining the final system properties. The addition of NPs could degrade the magnetic properties of the rod surface, which became magnetically softer, the strength of this effect depending on the coverage degree. In the case of ε -Fe₂O₃-Au, metal particles were mostly confined on the top of the rods, thus leading to a small effect, whereas lower sized CuO particles were distributed along the whole rod axes, increasing the amount of the softer phase and explaining thus the constricted hysteresis loop observed in this case.

To further disclose the effects of nanoparticle introduction, in-plane remanence magnetization studies were performed to investigate the magnetic interactions between the rods. Both Isothermal Remanent Magnetization (IRM) and Direct Current Demagnetization (DCD) remanent magnetization curves were measured (Fig. 6a). The initial state for an IRM measurement is a totally demagnetized sample cooled in zero magnetic field. In the present case, an external field was applied for 10 s; subsequently, it was switched off and the remanence was measured (M_{IRM}). The process was repeated, increasing the field up to 2 T. In a DCD measurement, the initial state is the magnetically saturated one. An external field of -2 T was applied for 10 s; then, a small external field in the direction opposite to magnetization was applied and, after 10 s, it was switched off and the remanent magnetization (M_{DCD}) was measured. By differentiating the two remanence curves with respect to the field, it is possible to obtain the irreversible susceptibility χ_{irr} . The latter represents a map of the switching field distribution in both IRM and DCD modes where the switching field is the magnetic field needed to irreversibly revert the magnetization. For an ideal, non-interacting system with uniaxial anisotropy the two differentiated curves should overlap, with a factor of 2 in the height of the $dM_{r,IRM}/dH$ relative to the $dM_{r,DCD}/dH$ curve derived from the Wohlfarth relation [51]:

$$M_{r,DCD} = 1 - 2 M_{r,IRM} \quad (3)$$

In a real system, any deviation from this relationship can be attributed to the effect of magnetic interactions as proposed by Kelly [52], who expressed the parameter δM as:

$$\delta M = M_{r,DCD} - (1 - 2 M_{r,IRM}) \quad (4)$$

Positive δM values can be attributed to interactions promoting the magnetized state (exchange interactions), whereas negative δM values are due to demagnetizing interactions (e.g., dipole-dipole interactions) [53]. It is worth recalling that exchange interactions imply a direct contact between magnetic elements, whereas the dipolar interactions are long-range ones and are directly (inversely) proportional to the moment (distance). The remanence measurements (Fig. 6b) indicated that dipolar interactions were

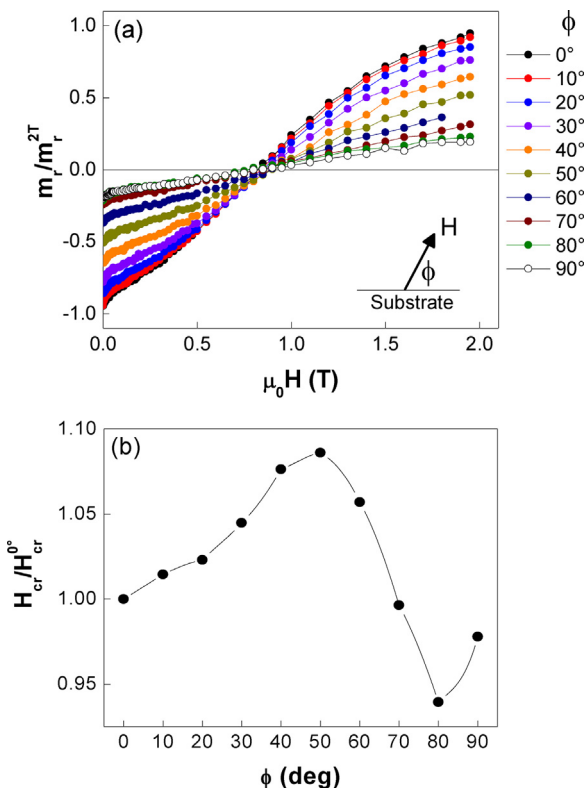


Fig. 7. (a) Set of DCD curves of sample ε -Fe₂O₃-Au measured with the external field applied at different ϕ angles with respect to the substrate surface. (b) Angular dependence of the experimental normalized remanence coercivity $H_{cr}(\phi)/H_{cr}(0^\circ)$.

predominant in all the samples (negative δM), the absolute value of δM (i.e., the interaction strength) being larger for ε -Fe₂O₃-Au ($\delta M \approx 0.31$) and lower for ε -Fe₂O₃-CuO ($\delta M \approx 0.24$). The lower dipolar interaction strength in the ε -Fe₂O₃-CuO sample could be a consequence of a magnetization decrease due to a variation of magnetic properties at the rod surface. In order to attain a deeper insight into the sample magnetic behavior, the magnetization reversal (or switching) mechanism of sample Fe₂O₃-Au, which presents a nearly single-phase behavior, was investigated by measuring a set of DCD curves at different ϕ angles (ranging between 0° and 90°, Fig. 7a), ϕ being the angle between H and the magnetic easy-axis, i.e. the normal to the rod axis in the target case. The remanent curves allow purely irreversible magnetization changes to be investigated and are more appropriate to describe the switching process with respect to the hysteresis loops, that encompass both reversible and irreversible processes [54]. From each DCD curve, the remanent

coercivity H_{cr} , defined as the field at which the remanence is zero, was determined and its dependence on the angle ϕ (i.e., H_{cr} vs. ϕ) is reported in Fig. 7b. The observed trend suggested a highly incoherent magnetization reversal process, which can explain the lower values of coercivity (≈ 0.35 T) and remanence coercivity (≈ 0.75 T) with respect to the typical ones reported for randomly oriented single-domain ϵ -Fe₂O₃ nanoparticles reversing coherently [55].

4. Conclusions

The present contribution reported on the vapor phase preparation of ϵ -Fe₂O₃ nanorod arrays functionalized with Au (or CuO) nanoparticles. In particular, Si(100)-supported ϵ -Fe₂O₃ deposits were obtained by a CVD route, and functionalization with gold [or copper(II) oxide] NPs was subsequently performed by RF-sputtering under mild conditions. The obtained materials were characterized by the formation of oriented ϵ -Fe₂O₃ nanorod arrays, with Au NPs mainly concentrated in the outermost system region, whereas CuO nanoaggregates were distributed even in the inner ones. For the first time, the magnetic properties of supported ϵ -Fe₂O₃-Au and ϵ -Fe₂O₃-CuO composites were investigated, revealing the occurrence of various effects that could be attributed to the performed NPs functionalization. In particular, when the rods were decorated with Au nanoparticles, their magnetic properties remained almost unchanged, being the particles mainly confined on the top of the rods. In a different way, CuO NPs decorated the whole rod walls, leading to an appreciable variation of magnetic properties. The obtained results open attractive perspectives for further advancements of the present research activities, concerning a deeper insight into the relations between the NP nature/nano-organization and the resulting magnetic properties. Such studies can promote both fundamental and applied developments towards the exploitation of ϵ -Fe₂O₃, eventually functionalized by metallic of metal oxide NPs, in various technological applications, such as information storage devices, energy, telecommunications, and biomedicine.

Acknowledgements

G.C., C.M. and D.B. kindly acknowledge the financial support under the Padova University ex-60% 2013-2017, P-DiSC #SENSATIONAL BIRD2016-UNIPD projects and ACTION post-doc fellowship, as well as the assistance of Prof. E. Bontempi (Brescia University, Italy) in sample characterization. G.V. and D.P. are grateful to Mr. E. Patrizi for technical assistance in magnetic measurements.

References

- [1] M. Yoshikiyo, A. Namai, K. Nakagawa, S.-i. Ohkoshi, Magnetic glass-film based on single-nanosize, *AIP Adv.* 7 (2017) 056218.
- [2] G. Carraro, C. Maccato, A. Gasparotto, T. Montini, S. Turner, O.I. Lebedev, V. Gombac, G. Adami, G. Van Tendeloo, D. Barreca, P. Fornasiero, Enhanced hydrogen production by photoreforming of renewable oxygenates through nanostructured Fe₂O₃ polymorphs, *Adv. Funct. Mater.* 24 (2014) 372.
- [3] L.T. Quynh, C.N. Van, Y. Bitla, J.W. Chen, T.H. Do, W.Y. Tzeng, S.C. Liao, K.A. Tsai, Y.C. Chen, C.L. Wu, C.H. Lai, C.W. Luo, Y.J. Hsu, Y.H. Chu, Self-assembled BiFeO₃- ϵ -Fe₂O₃ vertical heteroepitaxy for visible light photoelectrochemistry, *Adv. Energy Mater.* 6 (2016), 1600686.
- [4] W. Wu, Q. He, C. Jiang, Magnetic iron oxide nanoparticles: synthesis and surface functionalization strategies, *Nanoscale Res. Lett.* 3 (2008) 397–415.
- [5] R. Cornell, U. Schwertmann, *The Iron Oxides*, 2nd ed., Wiley-VCH GmbH & Co., Weinheim, 2003.
- [6] G. Muscas, G. Singh, W.R. Glomm, R. Mathieu, P.A. Kumar, G. Concas, E. Agostinelli, D. Peddis, Tuning the size and shape of oxide nanoparticles by controlling oxygen content in the reaction environment: morphological analysis by aspect maps, *Chem. Mater.* 27 (2015) 1982–1990.
- [7] L. Suber, D. Peddis, Approaches to synthesis and characterization of spherical and anisometric metal oxide magnetic nanomaterials, in: C.S.S.R. Kumar (Ed.), *Nanomaterials for the Life Science*, 4, Wiley, 2009, pp. 431–487.
- [8] V.N. Nikolić, M. Tadić, M. Panjan, L. Kopanja, N. Cvjetičanin, V. Spasojević, Influence of annealing treatment on magnetic properties of Fe₂O₃/SiO₂ and formation of ϵ -Fe₂O₃ phase, *Ceram. Int.* 43 (2017) 3147–3155.
- [9] D.A. Balaev, S.S. Yakushkin, A.A. Dubrovskii, G.A. Bukhtiyarova, K.A. Shaikhutdinov, O.N. Martyanov, Study of the high-coercivity material based on ϵ -Fe₂O₃ nanoparticles in the silica gel matrix, *Tech. Phys. Lett.* 42 (2016) 347–350.
- [10] A. Sivkov, E. Naiden, A. Ivashutenko, I. Shanenkov, Plasma dynamic synthesis and obtaining ultrafine powders of iron oxides with high content of ϵ -Fe₂O₃, *J. Magn. Magn. Mater.* 405 (2016) 158–168.
- [11] D. Korte, G. Carraro, F. Fresno, M. Franko, Thermal properties of surface-modified α - and ϵ -Fe₂O₃ photocatalysts determined by beam deflection spectroscopy, *Int. J. Thermophys.* 35 (2014) 2107–2114.
- [12] C. Cannas, A. Ardu, D. Niznansky, D. Peddis, G. Piccaluga, A. Musinu, Simple and fast preparation of pure maghemite nanopowders through sol-gel self-combustion, *J. Sol-Gel Sci. Technol.* 60 (2011) 266–274.
- [13] D. Barreca, G. Carraro, A. Gasparotto, C. Maccato, F. Rossi, G. Salvati, M. Tallarida, C. Das, F. Fresno, D. Korte, U. Lavrenčič Stangar, M. Franko, D. Schmeisser, Surface functionalization of nanostructured Fe₂O₃ polymorphs: from design to light-activated applications, *ACS Appl. Mater. Interfaces* 5 (2013) 7130–7138.
- [14] G. Carraro, A. Gasparotto, C. Maccato, V. Gombac, F. Rossi, T. Montini, D. Peeters, E. Bontempi, C. Sada, D. Barreca, P. Fornasiero, Solar H₂ generation via ethanol photoreforming on epsilon-Fe₂O₃ nanorod arrays activated by Ag and Au nanoparticles, *RSC Adv.* 4 (2014) 32174–32179.
- [15] G. Carraro, D. Barreca, C. Maccato, E. Bontempi, L.E. Depero, C. de Julián Fernández, A. Caneschi, Supported ϵ and β iron oxide nanomaterials by chemical vapor deposition: structure, morphology and magnetic properties, *CrystEngComm* 15 (2013) 1039–1042.
- [16] S.-i. Ohkoshi, A. Namai, T. Yamaoka, M. Yoshikiyo, K. Imoto, T. Nasu, S. Anan, Y. Umetsu, K. Nakagawa, H. Tokoro, Mesoscopic bar magnet based on ϵ -Fe₂O₃ hard ferrite, *Sci. Rep.* 6 (2016) 27212.
- [17] O.S. Ivanova, R.D. Ivantsov, I.S. Edelman, E.A. Petrakovskaja, D.A. Velikanov, Y.V. Zubavichus, V.I. Zaikovskii, S.A. Stepanov, Identification of ϵ -Fe₂O₃ nano-phase in borate glasses doped with Fe and Gd, *J. Magn. Magn. Mater.* 401 (2016) 880–889.
- [18] J.I. Tuček, R. Zbořil, A. Namai, S.-i. Ohkoshi, ϵ -Fe₂O₃: an advanced nanomaterial exhibiting giant coercive field, millimeter-wave ferromagnetic resonance, and magnetoelectric coupling, *Chem. Mater.* 22 (2010) 6483–6505.
- [19] S.N. Bahadur, A. Sonal, Nanocomposites: an overview, *Emerging Mater. Res.* 5 (2016) 5–43.
- [20] M. Mikhaylova, D.K. Kim, N. Bobrysheva, M. Osmolowsky, V. Semenov, T. Tsakalacos, M. Muhammed, Superparamagnetism of magnetite nanoparticles: dependence on surface modification, *Langmuir* 20 (2004) 2472–2477.
- [21] J.L. Lyon, D.A. Fleming, M.B. Stone, P. Schiffer, M.E. Williams, Synthesis of Fe oxide core/Au shell nanoparticles by iterative hydroxylamine seeding, *Nano Lett.* 4 (2004) 719–723.
- [22] D. Korte, G. Carraro, C. Maccato, M. Franko, Determination of thermo-optical and transport parameters of ϵ iron(III) oxide-based nanocomposites by beam deflection spectroscopy, *Opt. Mater.* 42 (2015) 370–375.
- [23] Z. Xu, Y. Hou, S. Sun, Magnetic core/shell Fe₃O₄/Au and Fe₂O₄/Au/Ag nanoparticles with tunable plasmonic properties, *J. Am. Chem. Soc.* 129 (2007) 8698–8699.
- [24] L. Wang, J. Luo, Q. Fan, M. Suzuki, I.S. Suzuki, M.H. Engelhard, Y. Lin, N. Kim, J.Q. Wang, C.-J. Zhong, Monodispersed core-shell Fe₃O₄@Au nanoparticles, *J. Phys. Chem. B* 109 (2005) 21593–21601.
- [25] D. Paul Joseph, C. Venkateswaran, R. Selva Vennila, Critical analysis on the structural and magnetic properties of bulk and nanocrystalline Cu-Fe-O, *Adv. Mater. Sci. Eng.* 2010 (2010) 715872.
- [26] S.J. Stewart, R.A. Borzi, G. Punte, R.C. Mercader, F. Garcia, Microstructural and magnetic characterization of nanostructured α -Fe₂O₃ and CuO mixtures obtained by ball milling, *J. Phys.: Condens. Matter* 13 (2001) 1743–1757.
- [27] D. Barreca, P. Fornasiero, A. Gasparotto, V. Gombac, C. Maccato, T. Montini, E. Tondello, The potential of supported Cu₂O and CuO nanosystems in photocatalytic H₂ production, *ChemSusChem* 2 (2009) 230–233.
- [28] D. Barreca, G. Carraro, E. Comini, A. Gasparotto, C. Maccato, C. Sada, G. Sberveglieri, E. Tondello, Novel synthesis and gas sensing performances of CuO-TiO₂ nanocomposites functionalized with Au nanoparticles, *J. Phys. Chem. C* 115 (2011) 10510–10517.
- [29] Y.S. Chaudhary, A. Agrawal, R. Shrivastav, V.R. Satsangi, S. Dass, A study on the photoelectrochemical properties of copper oxide thin films, *Int. J. Hydrogen Energy* 29 (2004) 131–134.
- [30] D. Barreca, A. Gasparotto, C. Maccato, E. Tondello, O.I. Lebedev, G. Van Tendeloo, CVD of copper oxides from a β -diketonate diamine precursor: tailoring the nano-organization, *Cryst. Growth Des.* 9 (2009) 2470–2480.
- [31] D. Saberi, M. Sheykhan, K. Niknam, A. Heydari, Preparation of carbon nanotube-supported α -Fe₂O₃@CuO nanocomposite: a highly efficient and magnetically separable catalyst in cross-coupling of aryl halides with phenols, *Catal. Sci. Technol.* 3 (2013) 2025–2031.
- [32] D. Barreca, G. Carraro, D. Peeters, A. Gasparotto, C. Maccato, W.M.M. Kessels, V. Longo, F. Rossi, E. Bontempi, C. Sada, A. Devi, Surface decoration of ϵ -Fe₂O₃ nanorods by CuO via a two-step CVD/sputtering approach, *Chem. Vap. Deposition* 20 (2014) 313–319.
- [33] S. Sakurai, A. Namai, K. Hashimoto, S.-i. Ohkoshi, First observation of phase transformation of all four Fe₂O₃ phases ($\gamma \rightarrow \epsilon \rightarrow \beta \rightarrow \alpha$ -phase), *J. Am. Chem. Soc.* 131 (2009) 18299–18303.

- [34] H.S. Nalwa, *Encyclopedia of Nanoscience and Nanotechnology*, vol. 1–10, American Scientific Publishers, Los Angeles CA, 2004.
- [35] G. Carraro, A. Gasparotto, C. Maccato, E. Bontempi, O.I. Lebedev, C. Sada, S. Turner, G. Van Tendeloo, D. Barreca, Rational synthesis of F-doped iron oxides on Al₂O₃(0001) single crystals, *RSC Adv.* 4 (2014) 52140–52146.
- [36] G. Carraro, C. Maccato, E. Bontempi, A. Gasparotto, O.I. Lebedev, S. Turner, L.E. Depero, G. Van Tendeloo, D. Barreca, Insights on growth and nanoscopic investigation of uncommon iron oxide polymorphs, *Eur. J. Inorg. Chem.* 2013 (2013) 5454–5461.
- [37] D. Peeters, D. Barreca, G. Carraro, E. Comini, A. Gasparotto, C. Maccato, C. Sada, G. Sberveglieri, Au/ ϵ -Fe₂O₃ nanocomposites as selective NO₂ gas sensors, *J. Phys. Chem. C* 118 (2014) 11813–11819.
- [38] D. Barreca, G. Carraro, A. Devi, E. Fois, A. Gasparotto, R. Seraglia, C. Maccato, C. Sada, G. Tabacchi, E. Tondello, A. Venzo, M. Winter, β -Fe₂O₃ nanomaterials from an iron(II) diketonate-diamine complex: a study from molecular precursor to growth process, *Dalton Trans.* 41 (2012) 149–155.
- [39] D. Barreca, A. Gasparotto, E. Tondello, C. Sada, S. Polizzi, A. Benedetti, Nucleation and growth of nanophasic CeO₂ thin films by plasma-enhanced CVD, *Chem. Vap. Deposition* 9 (2003) 199–206.
- [40] D. Briggs, M.P. Seah, *Practical Surface Analysis: Auger and X-ray Photoelectron Spectroscopy*, 2nd ed., John Wiley & Sons, New York, 1990.
- [41] J.F. Moulder, W.F. Stickle, P.E. Sobol, K.D. Bomben, *Handbook of X-ray Photoelectron Spectroscopy*, Perkin Elmer Corporation, Eden Prairie, MN, USA, 1992.
- [42] D.A. Shirley, High-resolution X-ray photoemission spectrum of the valence bands of gold, *Phys. Rev. B* 5 (1972) 4709–4714.
- [43] C.D. Wagner, A. Joshi, The Auger parameter, its utility and advantages: a review, *J. Electron. Spectrosc. Relat. Phenom.* 47 (1988) 283–313.
- [44] G. Moretti, Auger parameter and Wagner plot in the characterization of chemical states by X-ray photoelectron spectroscopy: a review, *J. Electron. Spectrosc. Relat. Phenom.* 95 (1998) 95–144.
- [45] <http://srdata.nist.gov/xps>.
- [46] Pattern N° 51122, ICSD, 2007.
- [47] R.A. Laudise, *Treatise on Solid State Chemistry*, Plenum Press, New York, 1975.
- [48] Y. Pan, Y. Gao, G. Wang, D. Kong, L. Zhang, J. Hou, S. Hu, H. Pan, J. Zhu, Growth structure, and stability of Au on ordered ZrO₂(111) thin films, *J. Phys. Chem. C* 115 (2011) 10744–10751.
- [49] S.-i. Ohkoshi, H. Tokoro, Hard magnetic ferrite: ϵ -Fe₂O₃, *Bull. Chem. Soc. Jpn.* 86 (2013) 897–907.
- [50] K.-h. Zhong, Z.-g. Huang, Z.-g. Chen, Q. Feng, Y.-m. Yang, Numerical calculation of magnetization behavior for Co nanowire array, *Trans. Nonferrous Met. Soc. China* 18 (2008) 700–706.
- [51] E.P. Wohlfarth, Relations between different modes of acquisition of the remanent magnetization of ferromagnetic particles, *J. Appl. Phys.* 29 (1958) 595–596.
- [52] P.E. Kelly, K.O. Grady, P.I. Mayo, R.W. Chantrell, Switching mechanisms in cobalt-phosphorus thin films, *IEEE Trans. Magn.* 25 (1989) 3881–3883.
- [53] D. Peddis, P.E. Jonsson, G. Varvaro, S. Laureti, in: C. Binns (Ed.), *Nanomagnetism: Fundamentals and Applications*, Elsevier B.V, Oxford, UK, 2014, pp. 129–189.
- [54] G. Muscas, P. Anil Kumar, G. Barucca, G. Concas, G. Varvaro, R. Mathieu, D. Peddis, Designing new ferrite/manganite nanocomposites, *Nanoscale* 8 (2016) 2081–2089.
- [55] J. Jin, S.-i Ohkoshi, K. Hashimoto, Giant coercive field of nanometer-sized iron oxide, *Adv. Mater.* 16 (2004) 48–51.