

Moiré-Induced Transport in CVD-Based Small-Angle Twisted Bilayer Graphene

Giulia Piccinini, Vaidotas Mišekis, Pietro Novelli, Kenji Watanabe, Takashi Taniguchi, Marco Polini, Camilla Coletti,* and Sergio Pezzini*



Cite This: *Nano Lett.* 2022, 22, 5252–5259



Read Online

ACCESS |


Metrics & More

Article Recommendations

Supporting Information

ABSTRACT: To realize the applicative potential of 2D twistronic devices, scalable synthesis and assembly techniques need to meet stringent requirements in terms of interface cleanliness and twist-angle homogeneity. Here, we show that small-angle twisted bilayer graphene assembled from separated CVD-grown graphene single-crystals can ensure high-quality transport properties, determined by a device-scale-uniform moiré potential. Via low-temperature dual-gated magnetotransport, we demonstrate the hallmarks of a 2.4° -twisted superlattice, including tunable regimes of interlayer coupling, reduced Fermi velocity, large interlayer capacitance, and density-independent Brown-Zak oscillations. The observation of these moiré-induced electrical transport features establishes CVD-based twisted bilayer graphene as an alternative to “tear-and-stack” exfoliated flakes for fundamental studies, while serving as a proof-of-concept for future large-scale assembly.

KEYWORDS: Twisted bilayer graphene, chemical vapor deposition, van der Waals assembly, moiré superlattice

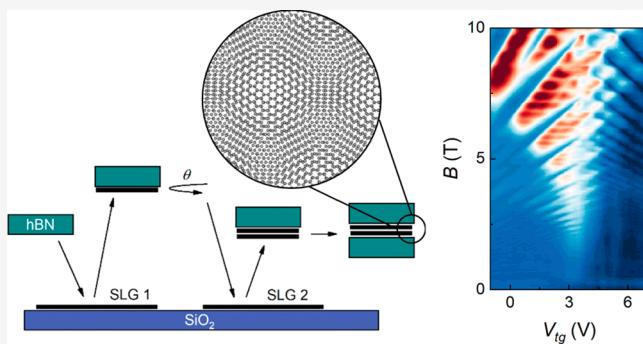

Twisted 2D materials provide an extraordinarily rich platform for engineering emergent electronic,^{1,2} magnetic,³ and optical⁴ properties. The van der Waals (vdW) stacking techniques,^{5,6} which are not applicable to traditional low-dimensional condensed-matter systems,⁷ are especially boosting this research field, allowing the realization of complex moiré structures involving multiple precisely aligned atomic layers.^{8–10} As twistronics, that is, the understanding and control of the moiré-induced behaviors, rapidly advances,^{11–13} novel perspectives of technological application arise.¹⁴ For instance, the tantalizing superconducting phase of magic-angle (MA) twisted bilayer graphene (TBG)¹ has already been exploited for the fabrication of broadband photodetectors,¹⁵ as well as gate-defined monolithic Josephson junctions^{16–18} and quantum interference devices.¹⁹ However, although technological integration of stand-alone 2D materials appears increasingly viable thanks to key advancements in the synthesis methods²⁰ (such as chemical vapor deposition (CVD) of high-mobility single-layer graphene (SLG)^{21–24}), in the case of TBG, further challenges have to be addressed. Ideally, application-oriented TBG devices should simultaneously offer (i) a deterministically selectable small-angle (SA) twisting, (ii) a device-scale uniform twist angle, and (iii) an atomically clean interlayer enabling the formation of a moiré potential. In TBG, strong modifications in the electronic bands arise only for SA twisting ($\theta < 5^\circ$),^{25,26} while the physics of two decoupled layers is reached asymptotically at larger twist angles.^{27–29} SA


twisting was observed in CVD-grown graphene films studied by scanning probe microscopy.³⁰ However, due to its polycrystalline nature and random grain orientations, this system is unsuitable for spatially averaging probes such as electrical transport. CVD-grown graphene single crystals, compatible with fabrication of high-quality devices, can incorporate TBG domains with uniform twisting.^{31–34} Nonetheless, the twist angle preferentially locks to 0° (Bernal stacking) or 30° due to interactions with the growth substrate.³¹

Recent developments in the synthesis process³⁵ have allowed one to obtain a fraction of intermediate twist-angles (down to $\sim 3^\circ$), higher than in previous studies³⁶ but lacking however deterministic control, as well as moiré transport signatures. To overcome this issue, one can employ a hybrid approach by stacking two CVD-grown SLG to form TBG, obtaining either large or SA twisting, as demonstrated by photoemission^{37–39} and scanning probe experiments,^{40,41} respectively. Although permitting high rotational accuracy in analogy to exfoliated flakes,⁶ sequentially stacked CVD-grown

Received: March 18, 2022

Revised: June 27, 2022

Published: July 1, 2022



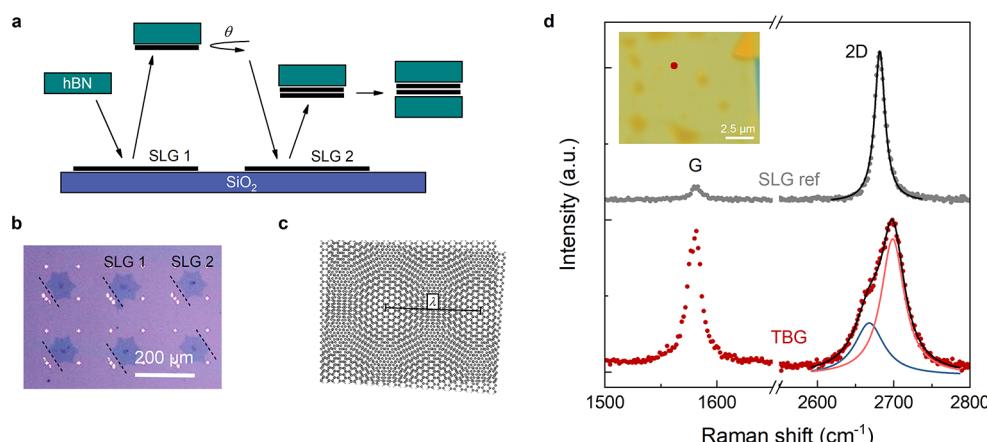


Figure 1. (a) Schematics of the dry pick-up process with stacking of separated CVD-grown graphene crystals. (b) Optical microscopy image of CVD SLG crystals on SiO₂/Si. The dashed lines indicate their crystallographic alignment. (c) The θ -rotated graphene sheets form a moiré pattern with periodicity λ . (d) Representative Raman spectrum of TBG (dark red), compared to a SLG reference (gray). The light red and blue lines are the two Lorentzian components of the TBG 2D peak. Inset: optical microscopy image of hBN-encapsulated SA-TBG. The dark red spot indicates the point where the TBG spectrum in the main panel is acquired.

graphene layers tend to damage and accumulate contaminants at their interface.⁴² As a consequence, transport experiments on CVD-based TBG with moiré effects are (to the best of our knowledge) unreported and, therefore a conclusive demonstration of TBG realizing the preliminary scalability conditions outlined above is lacking.

In this work, we fill this gap by introducing SA-TBG samples obtained by hBN-mediated stacking of isolated SLG crystals grown by CVD on a single Cu grain. The growth-determined crystallographic alignment of the SLG crystals⁴³ enables deterministic control on the twist angle at the vdW assembly stage. The interface cleanliness and twist-angle uniformity are unambiguously supported by the observation of high-quality quantum transport features specific to TBG with a twist angle of $\sim 2.4^\circ$. By these means, we demonstrate the first moiré device based on CVD-grown crystals and set a cornerstone toward the application of 2D materials twistronics.

In Figure 1a, we present the vdW assembly sequence developed for CVD-based SA-TBG. As the pick-up medium, we employ a poly(bisphenol A carbonate) (PC) film deposited onto a few-mm thick polydimethylsiloxane (PDMS) block, supported by a glass slide,⁴⁴ that we control using a home-built transfer setup.⁴⁵ We start from an array of SLG crystals grown via CVD on Cu (see the SI file for details) and subsequently transferred to SiO₂/Si using a polymer-assisted technique, as described in refs 43 and 45. We select two graphene crystals from the array, making sure that they were synthesized on the same Cu grain and, therefore, that they share the same crystallographic orientation, as demonstrated in ref 43 (Figure 1b). The use of two separated crystals extends the standard method for preparing SA-TBG samples for transport studies, which proceeds by stacking two portions of the same SLG flake.⁶ Once the two crystals are selected, we adopt the procedure described in ref 44 to pick up the first graphene crystal from SiO₂ using an hBN flake (10–50 nm thick). We then use the goniometer stage holding the sample with graphene on SiO₂ (shown in SI Figure S1) to rotate the graphene array by an arbitrary angle θ , which is affected by an instrumental error of $\sim 0.01^\circ$. The twist angle θ determines the expected periodicity λ of the moiré pattern (Figure 1c), according to $\lambda = \frac{a}{2 \sin(\frac{\theta}{2})}$, where $a \approx 0.246$ nm is the SLG

lattice constant. Thereafter, we approach and pick up the second graphene crystal and a second hBN flake, completing the encapsulation. The temperature of the setup is kept at 40–60°C during all these steps, consistently ensuring the complete pick-up of the graphene regions approached by the hBN. Finally, the stack is released onto a SiO₂/Si substrate by melting the PC film at 160–170°C, favoring cleaning of the vdW interfaces.⁴⁴ After the assembly, we nevertheless observe blisters where contaminants aggregate (Figure 1d, inset), which limit the lateral dimension of flat areas suitable for device processing (typically few micron-wide). Figure 1d shows the Raman spectrum of the assembled TBG, compared to that of an hBN-encapsulated SLG. The two spectra differ in several features. The large 2D/G intensity ratio characteristic of SLG (~ 10) dramatically drops in TBG (~ 1). In addition, the 2D peak width strongly increases, from ~ 17 to ~ 54 cm⁻¹. At a closer inspection, the 2D peak of TBG reveals a multicomponent structure^{46–48} with two broad subpeaks located at ~ 2675 and ~ 2700 cm⁻¹. Overall, we observe striking similarities with the Raman spectrum at $\sim 2.6^\circ$ -twisting reported in ref 46 in accordance with the angle $\theta = 2.5^\circ$ set during the vdW assembly. The assembly of a second sample with the same target angle, showing analogous Raman response, is presented in SI. Raman data from a third sample with sub-MA twisting are shown in SI.

The target angle θ is chosen to fall in the intermediate twist-angle range where the Fermi velocity (v_F) is reduced with respect to that of SLG,²⁵ while the interlayer coupling can be varied from weak to strong by experimentally available gate voltages. Such tunability was demonstrated by transport experiments on devices obtained by “tear-and-stack” exfoliated flakes in refs 47–51, which serve as a guideline for our investigation of CVD-based SA-TBG.

In Figure 2, we show low-temperature (magneto)transport data on a dual-gated device fabricated from the SA-TBG sample (see SI for details on the processing). The dual-gated configuration (Figure 2b) is essential in multilayer graphene devices, as it allows independent tuning of the total carrier density (n_{tot} determined by the sum of the gate potentials) and its distribution among the layers via the so-called displacement field (D , determined by the difference of the gate potentials). However, this holds true as long as the interlayer coupling is

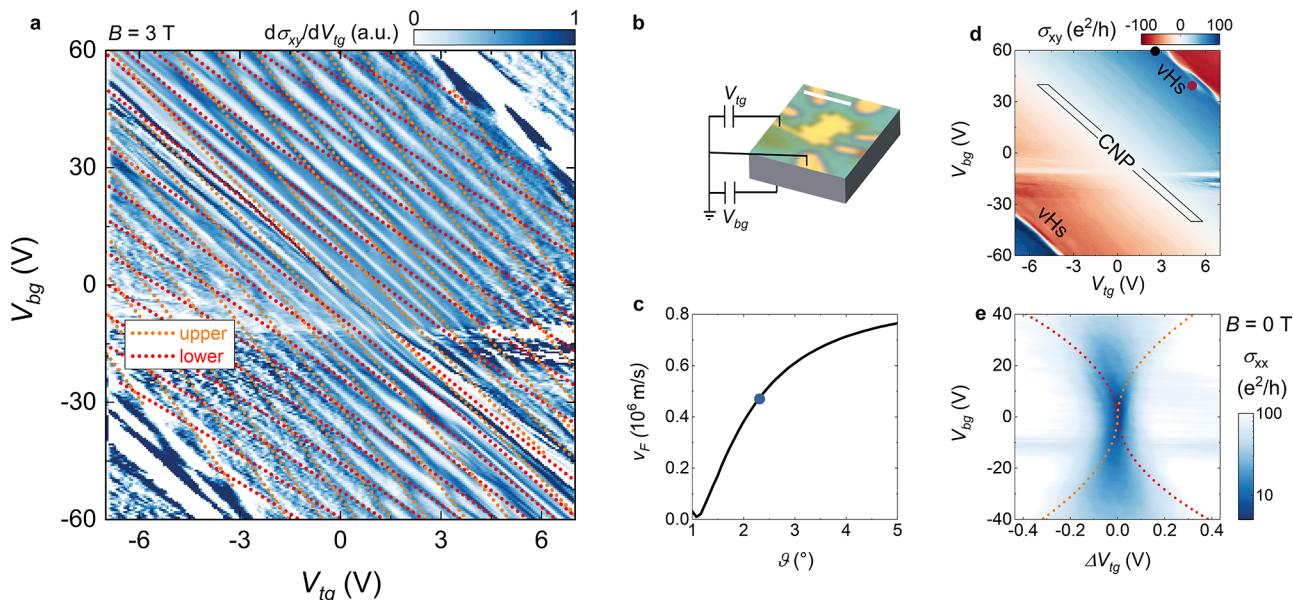


Figure 2. (a) First derivative of the Hall conductivity as a function of top and back-gate voltages, measured for a fixed value of the applied perpendicular magnetic field ($B = 3 \text{ T}$). The dotted orange (red) lines are the calculated positions of Landau levels from the upper (lower) graphene layers, employing $v_F = 0.47 \times 10^6 \text{ m/s}$ and $C_{gg} = 17.5 \times 10^{-6} \text{ F/cm}^2$. (b) Schematics of the gating configuration. The optical microscopy image of the device is taken before the final etching step; the scale bar is $2.5 \mu\text{m}$. (c) Fermi velocity of TBG as a function of the twist angle, calculated according to the theory described in refs 54 and 55 and references therein. Results in this figure have been obtained by setting $u_0 = 79.7 \text{ meV}$ and $u_1 = 97.5 \text{ meV}$, where u_0 and u_1 are the intra- and intersublattice interlayer tunneling amplitudes, respectively. The blue circle corresponds to the v_F value estimated for our device. (d) Hall conductivity as a function of the gate voltages (same gate ranges and magnetic field as in (a)). The sign changes in σ_{xy} correspond to the sample CNP and the two vHs. The black rectangle indicates the gate range considered in panel (e), the black and dark red dots are the gate values used for the measurements in Figure 4. (e) Zero-field longitudinal conductivity (lg scale) as a function of top-gate voltage relative to the sample CNP and back-gate voltage. The dotted orange (red) line is the calculated charge neutrality point for the upper (lower) layer. All the data in this figure have been acquired at $T = 4.2 \text{ K}$.

small enough as to keep the layers' Dirac cones independent,^{27–29,34} while in the strong coupling regime D has no major effect.⁵² By applying a perpendicular magnetic field ($B = 3 \text{ T}$ in Figure 2a) we observe a pattern of crossings in the derivative of the Hall conductivity σ_{xy} with respect to the voltage applied via the top gate ($d\sigma_{xy}/dV_{tg}$), corresponding to alternating interlayer quantum Hall states ($d\sigma_{xy}/dV_{tg} = 0$) and layer-resolved Landau levels (LLs, $d\sigma_{xy}/dV_{tg} \neq 0$).³⁴ This pattern can be modeled by considering the screening properties of two superimposed SLG subject to the top and bottom gate potentials— V_{tg} and V_{bg} , respectively—and coupled via an interlayer capacitance C_{gg} (complete details on the electrostatic model employed can be found in ref 53). Importantly, the exact gate dependence of the LLs is sensitive to both the carrier density n and Fermi energy E_F in the individual layers, which for Dirac Fermions are related according to $E_F = \hbar v_F \sqrt{\pi n}$. Using C_{gg} and v_F as free parameters, we simulate the LLs trajectories and make them converge to the experimental pattern of crossings. The results are shown as orange and red dotted lines in Figure 2a, for the upper and lower layers LLs, respectively. From this procedure, we can estimate a Fermi velocity $v_F = (0.47 \pm 0.02) \times 10^6 \text{ m/s}$ and an interlayer capacitance $C_{gg} = (17.5 \pm 1.0) \times 10^{-6} \text{ F/cm}^2$.

The suppression of v_F with respect to SLG is a well-known feature of SA-TBG.^{25,30} Band structure calculations based on Bistritzer-MacDonald-type Hamiltonians^{25,54,55} allow to estimate the corresponding twist angle to be $\sim 2.4^\circ$ (Figure 2c).

Concerning the interlayer capacitance and in agreement with ref 48, our estimate is twice as large with respect to the accepted value of C_{gg} for large-angle TBG.^{27,29} If one insists in using a classical-type formula for C_{gg} that is, $C_{gg} = \epsilon_0 \epsilon_r / d_{\text{eff}}$

with d_{eff} a suitable effective interlayer distance, this finding could be interpreted in terms of a smaller effective interlayer spacing, signaling the increased coupling in this twist-angle range (eventually, toward MA such effective separation vanishes, leading to a complete suppression of the LLs crossings⁵²). A less naive approach should rely on analyzing microscopically all the nonclassical contributions to C_{gg} by using the profound relationship that exists between the ground-state energy of a double-layer system and linear response functions.⁵⁶ This has been recently done for example in ref 57, but no explicit calculations have been reported by the authors for TBG.

The crossing pattern in Figure 2a is abruptly interrupted in the vicinity of the upper right and lower left corners of the V_{tg} – V_{bg} map, that is, at high total carrier density ($n_{\text{tot}} > 5.88 \times 10^{12} \text{ cm}^{-2}$ with n_{tot} being the sum of the carrier densities in the two layers obtained from the electrostatic modeling). The Hall conductivity σ_{xy} , plotted in Figure 2d, shows that the upper right (lower left) region corresponds to a transition from large electron (hole) density to large hole (electron) density. This change contrasts with the low-density switch at the charge-neutrality point (CNP, central diagonal), and it is characteristic of van Hove singularities (vHs) in the density of states, corresponding to the transition from layer-independent massless electrons (holes) to layer-coupled massive holes (electrons).^{47–51} In Figure 2e, we show the zero-field longitudinal conductivity as a function of the gate potentials in the vicinity of the sample CNP (black-highlighted area in Figure 2d). In this zoomed plot, we can observe different regions of interlayer charge configuration, controlled by a splitting of the CNPs of the individual layers (similar data for

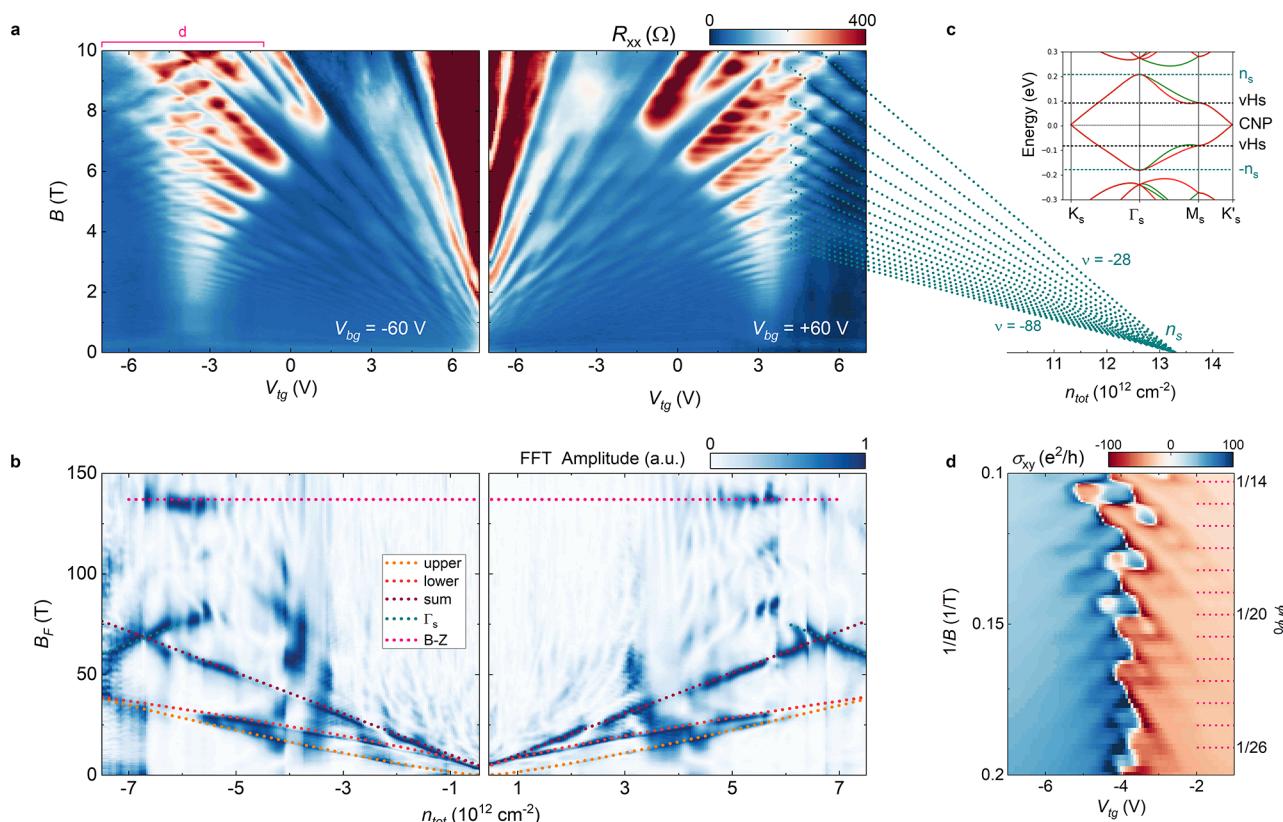


Figure 3. (a) Longitudinal resistance measured as a function of V_{tg} and B , at $V_{bg} = -60$ V (left panel, $T = 2.5$ K) and $V_{bg} = +60$ V (right panel, $T = 4.2$ K). (b) Normalized FFT amplitude of the data in panel (a), as a function of the total charge density and of the oscillation frequency B_F . (c) Fan of quantized states originating from the Γ_s point. Inset: band structure calculations for TBG with $\theta = 2.4^\circ$, based on refs 25, 54, and 55. The same intra- and intersublattice interlayer tunneling amplitudes of Figure 2c are used. Hartree self-consistent corrections do not yield significant changes with respect to single-particle calculations because the twist angle considered in this work is sufficiently larger than the MA. (d) Hall conductivity in the vicinity of the hole-side vHs, as a function of V_{tg} and $1/B$ (left axis). The right axis scale shows the number of flux quanta per superlattice unit cell, that is, ϕ/ϕ_0 .

large-angle TBG have been reported in refs 53 and 58). The boundaries of these regions are perfectly reproduced by the neutrality conditions for the two layers (orange and red dotted lines), computed according to the extracted v_F and C_{gg} , confirming the estimate obtained in the perpendicular magnetic field (in the SI file we show how the CNPs trajectories vary as functions of v_F and C_{gg}). The observation of the CNPs splitting substantiates the reduction of the peak resistance at large displacement fields observed in previous experiments^{47,50,51} which is due to coexisting charges of opposite sign in the two layers with relatively small concentration ($< 10^{11}$ cm\$^{-2}\$).

In Figure 3a we present the longitudinal resistance of the device, measured as a function of V_{tg} and B , at two fixed values of V_{bg} (-60 V and +60 V, in the left and right panels, respectively, corresponding to the upper and lower limits of the gate map in Figure 2a). This configuration is chosen to span the largest possible density range, while keeping D finite. A fast Fourier transform (FFT) of these data, giving the frequency spectrum of the $1/B$ -periodic components of the resistance,⁴⁷ is shown in Figure 3b to ease the interpretation of the complicated pattern of experimental data reported in Figure 3a. The color map in Figure 3b represents the normalized amplitude of the FFT plotted as a function of the total carrier density, and the frequency B_F which is proportional to the extremal area of the Fermi surface perpendicular to the magnetic field. In the central part of the magneto-resistance

data, close to the CNP, we observe two superimposed Landau fans, which can be attributed to the upper and lower layers' Dirac cones centered at the K_s and K'_s points in the superlattice Brillouin zone (see band structure calculations in Figure 3c, inset). Because of the finite displacement field, the two layers have different carrier concentrations and, therefore, the fans repeatedly cross each other. The corresponding frequencies in the FFT are well described by $B_F^{\text{layer}} = \frac{h}{4e}|n_{\text{layer}}|$ (orange and red dotted lines in Figure 3b, for the upper and lower layer, respectively), where the carrier concentration n_{layer} in each layer can be calculated by using the v_F and C_{gg} values extracted previously, and the factor 4 accounts for the spin and valley degeneracies. The sum of the two components evolves as $B_F^{\text{sum}} = \frac{h}{4e}|n_{\text{tot}}|$ (dark red dotted line).

At the largest density reached in the experiment (left-most part in the left panel, right-most part in the right one), we observe LL fans with opposite dispersions with respect to the central ones, in accordance with the change in sign of the charge carriers detected in the Hall conductivity (Figure 2d). These features emerge due to progressive filling of the moiré band at Γ_s (Figure 3c, inset), which is completed at $n_{\text{tot}} \equiv n_s = \frac{8}{\sqrt{3}\lambda^2}$. In Figure 3b we show that the frequency components corresponding to the Γ_s fans evolve as $B_F^{\Gamma_s} = \frac{h}{4e}|n_{\text{tot}} - n_s|$ (dark cyan dotted lines, where $n_s = \pm 13.3$

$\times 10^{12}$ cm $^{-2}$ for the right and left panel, respectively), indicating a single 4-fold degenerate Fermi surface, in agreement with ref 47. In Figure 3c, we show that the corresponding fan of quantized states, calculated using a zero Berry phase,⁴⁸ matches the resistance oscillations in panel a.

Close to the previously identified vHs ($V_{tg} \sim -4$ V and +4 V, in the left and right panel, respectively) we observe two funnelling structures with large longitudinal resistance, associated with the coexistence of carriers with opposite sign. Here, the oppositely dispersing fans of Landau levels coalesce, as expected from theoretical calculations in our twist-angle range.^{26,59} Notably, we observe a series of horizontal strikes superimposed to the intersecting fans, which signal a density-independent oscillation of the resistance. The corresponding frequency is equal to 137 T (magenta dotted line in Figure 3b). Density-independent oscillations were discovered in graphene-hBN superlattices^{60–62} and attributed to the periodic creation of so-called Brown-Zak (B-Z) particles moving along straight trajectories in finite magnetic field.⁶¹ The characteristic frequency of this phenomenon allows a highly precise estimate of the moiré periodicity according to $B_F^{BZ} = \frac{h}{e\sqrt{3}\lambda}$. Considering the average position of our FFT peak, we obtain a twist angle $\theta = (2.39 \pm 0.01)^\circ$. Finally, in Figure 3d we show the Hall conductivity in the vicinity of the hole-side vHs, as a function of $1/B$. In accordance to the B-Z periodicity, we observe sign changes at commensurate values of flux quanta per superlattice unit cell $\phi/\phi_0 = 1/q$ (where $\phi_0 = h/e$ is the flux quantum, and q is an integer). In addition, toward the highest magnetic fields, we observe a nonmonotonic behavior as a function of both magnetic field and carrier density, a hallmark of the Hofstadter's butterfly.^{63–65} The appearance of these features coincides with the transition from the semi-classical regime (well-defined electron and hole-like oscillations) to the fractal regime, which is expected when the magnetic length ($l_B \beta \sim \frac{25 \text{ nm}}{\sqrt{B[\text{T}]}}$) becomes comparable to the superlattice periodicity $\lambda = 5.9$ nm.²⁶

A distinctive feature of the B-Z oscillations is their resilience to the thermal energy, which allows their observation up to boiling-water temperature.⁶⁰ In Figure 4, we present resistance data acquired at $T = 35$ K, where the standard Shubnikov–De Haas oscillations are strongly suppressed and the B-Z oscillations become more apparent.⁵⁰ We show two curves taken in the vicinity of the electron-side vHs, at $D = 0$ and $D > 0$ (dark red and black curves, respectively; the gate values are indicated by markers in Figure 2d). We observe a dominant fast oscillation corresponding to the B-Z frequency ($B_F = 137$ T, see FFT spectra in the inset), whose amplitude and phase are unaffected by D (in addition to n_{tot} , as already shown in Figure 3b). This contrasts with the slowly varying background ($B_F \sim 30$ T), attributed to the K_s – K'_s Shubnikov–De Haas oscillations, whose phase reverts as a function of D as the charge distribution in the two layers is modified. Recently discovered D -dependent high-temperature oscillations from interminervalley scattering⁶⁶ are not observable in our current set of data.

The experimental observation of this collection of moiré-induced transport features necessarily implies the presence of a superlattice with uniform twist angle (within cent-of-degree accuracy) over the device area within the voltage probes ($\sim 2 \mu\text{m}^2$). While local techniques have been successfully applied before to CVD-based SA-TBG,⁴⁰ transport studies are not

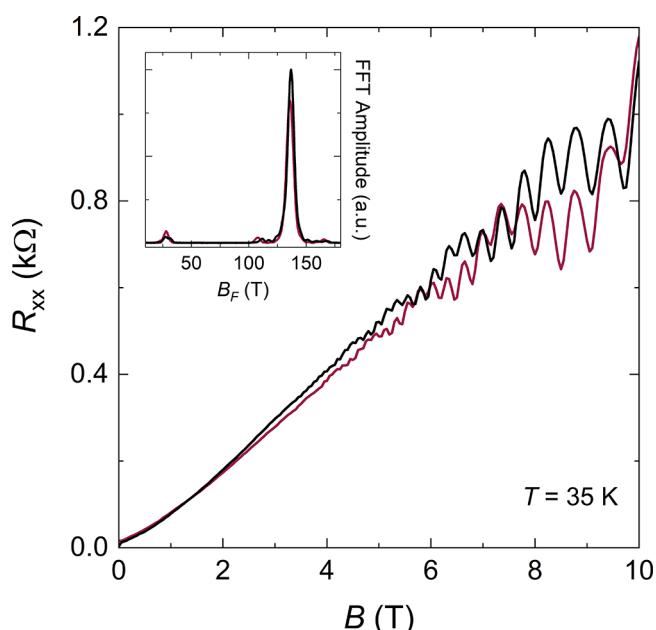


Figure 4. Longitudinal resistance as a function of B , measured at $T = 35$ K in the vicinity of the electron-side vHs, at $D = 0$ (dark red curve) and $D > 0$ (black curve); the gate values are indicated by the dark red and black circles in Figure 2d. Inset: FFT spectra of the oscillatory resistance from the curves in the main panel.

available in the literature, to the best of our knowledge. The realization of device-scale moiré effects using CVD-grown crystals is of high relevance for different potential applications. In particular, TBG can be used for ultrafast, highly sensitive and selective photodetectors.^{15,67} Moreover, moiré patterns in SA-TBG provide confined conducting channels that can be used for the directed propagation of surface plasmons⁶⁸ or for the study of moiré plasmons.^{54,55,69}

In principle, our assembly approach could be up-scaled by employing multiple crystals from the same array simultaneously (that is, within the same pick-rotate-and-stack process). Nonetheless, two main limiting factors to scalability of CVD-based SA-TBG should be considered. First, the presence of blisters due to incomplete interface cleaning currently constrain the device dimensions: this could be mitigated by using dry polymer-free techniques for CVD graphene transfer, such as in ref 21. Second, the requirement of hBN flakes, acting both as pick-up carrier and high-quality electrostatic environment for TBG, which are limited to the lateral size currently yielded by micromechanical exfoliation (typically up to $\sim 100 \mu\text{m}$).

In addition, while a path toward twisted N -layer graphene devices appears to be traced by recent results on flake-based quadrilaterals and pentalayers,^{70,71} a crucial experimental bottleneck arises. Exfoliated graphene flakes have limited lateral dimensions (up to $\sim 100 \mu\text{m}$), which impede the realization of thick angle-controlled stacks with areas compatible with device fabrication. Since our CVD matrixes retain a single crystallographic orientation over millimeters-sized areas, stacking of graphene layers with $N > 5$ and device-compatible size could be pursued using the technique introduced here.

In conclusion, we demonstrated the first SA-TBG high-quality moiré device based on CVD-grown crystals. The use of aligned graphene crystals from CVD-grown arrays, together

with the manual stacking approach, allows deterministically selectable twist angles. The existence of a moiré potential with uniform periodicity on a device-scale area is confirmed by the observation of density-independent Brown-Zak oscillations, which coexist with multiple Landau fans at low temperature, and survive up to tens of Kelvin. Overall, our results establish a novel tool for future developments of 2D materials twistronics and related technology.

■ ASSOCIATED CONTENT

SI Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acs.nanolett.2c01114>.

Details on the experimental methods for CVD growth, Raman spectroscopy, device fabrication, and low-temperature magnetotransport; assembly of a second SA-TBG sample; Raman and transport data on CVD-based bilayer graphene with sub-MA twisting; dependence of the CNPs splitting on Fermi velocity and interlayer capacitance; Figures S1–S4 ([PDF](#))

■ AUTHOR INFORMATION

Corresponding Authors

Camilla Coletti — *Center for Nanotechnology Innovation @ NEST, Istituto Italiano di Tecnologia, 56127 Pisa, Italy; Graphene Laboratories, Istituto Italiano di Tecnologia, 16163 Genova, Italy;*  [0000-0002-8134-7633](https://orcid.org/0000-0002-8134-7633); Email: camilla.coletti@iit.it

Sergio Pezzini — *NEST, Istituto Nanoscienze-CNR and Scuola Normale Superiore, 56127 Pisa, Italy;*  [0000-0003-4289-907X](https://orcid.org/0000-0003-4289-907X); Email: sergio.pezzini@nano.cnr.it

Authors

Giulia Piccinini — *NEST, Scuola Normale Superiore, 56127 Pisa, Italy; Center for Nanotechnology Innovation @NEST, Istituto Italiano di Tecnologia, 56127 Pisa, Italy;*  [0000-0002-2902-1361](https://orcid.org/0000-0002-2902-1361)

Vaidotas Mišekis — *Center for Nanotechnology Innovation @ NEST, Istituto Italiano di Tecnologia, 56127 Pisa, Italy; Graphene Laboratories, Istituto Italiano di Tecnologia, 16163 Genova, Italy*

Pietro Novelli — *Istituto Italiano di Tecnologia, 16152 Genova, Italy;*  [0000-0003-1623-5659](https://orcid.org/0000-0003-1623-5659)

Kenji Watanabe — *Research Center for Functional Materials, National Institute for Materials Science, Tsukuba 305-0044, Japan;*  [0000-0003-3701-8119](https://orcid.org/0000-0003-3701-8119)

Takashi Taniguchi — *International Center for Materials Nanoarchitectonics, National Institute for Materials Science, Tsukuba 305-0044, Japan;*  [0000-0002-1467-3105](https://orcid.org/0000-0002-1467-3105)

Marco Polini — *Dipartimento di Fisica, Università di Pisa, 56127 Pisa, Italy; Graphene Laboratories, Istituto Italiano di Tecnologia, 16163 Genova, Italy*

Complete contact information is available at:

<https://pubs.acs.org/10.1021/acs.nanolett.2c01114>

Notes

The authors declare no competing financial interest.

■ ACKNOWLEDGMENTS

We thank F. Rossella for technical support during the low-temperature experiments. Growth of hexagonal boron nitride

crystals was supported by the Elemental Strategy Initiative conducted by the MEXT, Japan, Grant JPMXP0112101001, JSPS KAKENHI Grant JP20H00354 and the CREST(JPMJCR15F3), JST. The research leading to these results has received funding from the European Union's Horizon 2020 research and innovation program under Grant Agreements 785219-Graphene Core2 and 881603-Graphene Core3.

■ REFERENCES

- (1) Cao, Y.; et al. Unconventional superconductivity in magic-angle graphene superlattices. *Nature* **2018**, *556*, 43–50.
- (2) Cao, Y.; et al. Correlated insulator behaviour at half-filling in magic-angle graphene superlattices. *Nature* **2018**, *556*, 80–84.
- (3) Sharpe, A. L.; et al. Emergent ferromagnetism near three-quarters filling in twisted bilayer graphene. *Science* **2019**, *365*, 605–608.
- (4) Tran, K.; et al. Evidence for moiré excitons in van der Waals heterostructures. *Nature* **2019**, *567*, 71–75.
- (5) Wang, L.; et al. One-dimensional electrical contact to a two-dimensional material. *Science* **2013**, *342*, 614–617.
- (6) Kim, K.; et al. van der Waals heterostructures with high accuracy rotational alignment. *Nano Lett.* **2016**, *16*, 1989–1995.
- (7) Geim, A. K.; Grigorieva, I. V. Van der Waals heterostructures. *Nature* **2013**, *499*, 419–425.
- (8) Wang, Z.; Wang, Y. B.; Yin, J.; Tovari, E.; Yang, Y.; Lin, L.; Holwill, M.; Birkbeck, J.; Perello, D. J.; Xu, S.; Zultak, J.; Gorbachev, R. V.; Kretinin, A. V.; Taniguchi, T.; Watanabe, K.; Morozov, S. V.; Andelkovic, M.; Milovanovic, S. P.; Covaci, L.; Peeters, F. M.; Mishchenko, A.; Geim, A. K.; Novoselov, K. S.; Fal'ko, V. I.; Knothe, A.; Woods, C. R. Composite super-moiré lattices in double-aligned graphene heterostructures. *Sci. Adv.* **2019**, *5*, No. eaay8897.
- (9) Park, J. M.; Cao, Y.; Watanabe, K.; Taniguchi, T.; Jarillo-Herrero, P. Tunable strongly coupled superconductivity in magic-angle twisted trilayer graphene. *Nature* **2021**, *590*, 249–255.
- (10) Hao, Z.; et al. Electric field-tunable superconductivity in alternating-twist magic-angle trilayer graphene. *Science* **2021**, *371*, 1133–1138.
- (11) Carr, S.; Massatt, D.; Fang, S.; Cazeaux, P.; Luskin, M.; Kaxiras, E. Twistrionics: Manipulating the electronic properties of two-dimensional layered structures through their twist angle. *Phys. Rev. B* **2017**, *95*, No. 075420.
- (12) Ribeiro-Palau, R.; Zhang, C.; Watanabe, K.; Taniguchi, T.; Hone, J.; Dean, C. R. Twistable electronics with dynamically rotatable heterostructures. *Science* **2018**, *361*, 690–693.
- (13) Yang, Y.; Li, J.; Yin, J.; Xu, S.; Mullan, C.; Taniguchi, T.; Watanabe, K.; Geim, A. K.; Novoselov, K. S.; Mishchenko, A. In situ manipulation of van der Waals heterostructures for twistrionics. *Sci. Adv.* **2020**, *6*, No. eabd3655.
- (14) Polini, M.; et al. Materials and devices for fundamental quantum science and quantum technologies. *arXiv* 2201.09260, 2022, accessed 2022-06-27.
- (15) Seifert, P.; et al. Magic-Angle Bilayer Graphene Nanocalorimeters: Toward Broadband, Energy-Resolving Single Photon Detection. *Nano Lett.* **2020**, *20*, 3459–3464.
- (16) Rodan-Legrain, D.; et al. Highly tunable junctions and non-local Josephson effect in magic-angle graphene tunnelling devices. *Nat. Nanotechnol.* **2021**, *16*, 769–775.
- (17) de Vries, F. K.; et al. Gate-defined Josephson junctions in magic-angle twisted bilayer graphene. *Nat. Nanotechnol.* **2021**, *16*, 760–763.
- (18) Diez-Merida, J.; et al. Magnetic Josephson Junctions and Superconducting Diodes in Magic Angle Twisted Bilayer Graphene. *arXiv* 2110.01067, 2021, accessed 2022-06-27.
- (19) Portolés, E.; et al. A Tunable Monolithic SQUID in Twisted Bilayer Graphene. *arXiv* 2201.13276, 2022, accessed 2022-06-27.
- (20) Backes, C.; et al. Production and processing of graphene and related materials. *2D Mater.* **2020**, *7*, No. 022001.

- (21) Banszerus, L.; Schmitz, M.; Engels, S.; Dauber, J.; Oellers, M.; Haupt, F.; Watanabe, K.; Taniguchi, T.; Beschoten, B.; Stampfer, C. Ultrahigh-mobility graphene devices from chemical vapor deposition on reusable copper. *Sci. Adv.* **2015**, *1*, No. e1500222.
- (22) De Fazio, D.; et al. High-mobility, wet-transferred graphene grown by chemical vapour deposition. *ACS Nano* **2019**, *13*, 8926–8935.
- (23) Pezzini, S.; et al. High-quality electrical transport using scalable CVD graphene. *2D Mater.* **2020**, *7*, No. 041003.
- (24) Schmitz, M.; et al. Fractional quantum Hall effect in CVD-grown graphene. *2D Mater.* **2020**, *7*, No. 041007.
- (25) Bistritzer, R.; MacDonald, A. H. Moiré bands in twisted double-layer graphene. *Proc. Natl. Acad. Sci. U.S.A.* **2011**, *108*, 12233–12237.
- (26) Moon, P.; Koshino, M. Energy spectrum and quantum Hall effect in twisted bilayer graphene. *Phys. Rev. B* **2012**, *85*, 195458.
- (27) Sanchez-Yamagishi, J. D.; Taychatanapat, T.; Watanabe, K.; Taniguchi, T.; Yacoby, A.; Jarillo-Herrero, P. Quantum Hall Effect, Screening, and Layer-Polarized Insulating States in Twisted Bilayer Graphene. *Phys. Rev. Lett.* **2012**, *108*, No. 076601.
- (28) Sanchez-Yamagishi, J. D.; et al. Helical edge states and fractional quantum Hall effect in a graphene electron–hole bilayer. *Nat. Nanotechnol.* **2017**, *12*, 118–122.
- (29) Rickhaus, P.; Liu, M.-H.; Kurpas, M.; Kurzmann, A.; Lee, Y.; Overweg, H.; Eich, M.; Pisoni, R.; Taniguchi, T.; Watanabe, K.; Richter, K.; Ensslin, K.; Ihn, T. The electronic thickness of graphene. *Sci. Adv.* **2020**, *6*, No. eaay8409.
- (30) Lucian, A.; et al. Single-Layer Behavior and Its Breakdown in Twisted Graphene Layers. *Phys. Rev. Lett.* **2011**, *106*, 126802.
- (31) Yan, Z.; et al. Large Hexagonal Bi-and Trilayer Graphene Single Crystals with Varied Interlayer Rotations. *Angew. Chemie Int. Ed.* **2014**, *53*, 1565–1569.
- (32) Gao, Z.; et al. Crystalline bilayer graphene with preferential stacking from Ni–Cu gradient alloy. *ACS Nano* **2018**, *12*, 2275–2282.
- (33) Deng, B.; et al. Interlayer Decoupling in 30° Twisted Bilayer Graphene Quasicrystal. *ACS Nano* **2020**, *14*, 1656–1664.
- (34) Pezzini, S.; et al. 30°-Twisted Bilayer Graphene Quasicrystals From Chemical Vapor Deposition. *Nano Lett.* **2020**, *20*, 3313–3319.
- (35) Sun, Y.; Polani, S.; Luo, F.; Ott, S.; Strasser, P.; Dionigi, F. Hetero-site nucleation for growing twisted bilayer graphene with a wide range of twist angles. *Nat. Commun.* **2021**, *12*, 2391.
- (36) Lu, C.-C.; Lin, Y.-C.; Liu, Z.; Yeh, C.-H.; Suenaga, K.; Chiu, P.-W. Twisting Bilayer Graphene Superlattices. *ACS Nano* **2013**, *7*, 2587–2594.
- (37) Ohta, T.; Robinson, J. T.; Feibelman, P. J.; Bostwick, A.; Rotenberg, E.; Beechem, T. E. Evidence for Interlayer Coupling and Moiré Periodic Potentials in Twisted Bilayer Graphene. *Phys. Rev. Lett.* **2012**, *109*, 186807.
- (38) Tan, Z.; et al. Building Large-Domain Twisted Bilayer Graphene with van Hove Singularity. *ACS Nano* **2016**, *10*, 6725–6730.
- (39) Yang, S.-J.; et al. Wafer-Scale Programmed Assembly of One-Atom-Thick Crystals. *Nano Lett.* **2022**, *22*, 1518–1524.
- (40) Wong, D.; et al. Local spectroscopy of moiré-induced electronic structure in gate-tunable twisted bilayer graphene. *Phys. Rev. B* **2015**, *92*, 155409.
- (41) Ren, Y.-N.; et al. Spectroscopic Evidence for a Spin- and Valley-Polarized Metallic State in a Nonmagic-Angle Twisted Bilayer Graphene. *ACS Nano* **2020**, *14*, 13081–13090.
- (42) Shivayogimath, A.; et al. Do-It-Yourself Transfer of Large-Area Graphene Using an Office Laminator and Water. *Chem. Mater.* **2019**, *31*, 2328–2336.
- (43) Miseikis, V.; et al. Deterministic patterned growth of high-mobility large-crystal graphene: A path towards wafer scale integration. *2D Mater.* **2017**, *4*, No. 021004.
- (44) Purdie, D. G.; Pugno, N. M.; Taniguchi, T.; Watanabe, K.; Ferrari, A. C.; Lombardo, A. Cleaning interfaces in layered materials heterostructures. *Nat. Commun.* **2018**, *9*, 5387.
- (45) Giambra, M. A.; et al. Wafer-Scale Integration of Graphene-Based Photonic Devices. *ACS Nano* **2021**, *15*, 3171–3187.
- (46) Gadelha, A. C.; Ohlberg, D. A. A.; Rabelo, C.; Neto, E. G. S.; Vasconcelos, T. L.; Campos, J. L.; Lemos, J. S.; Ornelas, V.; Miranda, D.; Nadas, R.; Santana, F. C.; Watanabe, K.; Taniguchi, T.; van Troeye, B.; Lamparski, M.; Meunier, V.; Nguyen, V.-H.; Paszko, D.; Charlier, J.-C.; Campos, L. C.; Cancado, L. G.; Medeiros-Ribeiro, G.; Jorio, A. Localization of lattice dynamics in low-angle twisted bilayer graphene. *Nature* **2021**, *590*, 405–409.
- (47) Cao, Y.; et al. Superlattice-Induced Insulating States and Valley-Protected Orbitals in Twisted Bilayer Graphene. *Phys. Rev. Lett.* **2016**, *117*, 116804.
- (48) Chung, T.-F.; Xu, Y.; Chen, Y. P. Transport measurements in twisted bilayer graphene: Electron-phonon coupling and Landau level crossing. *Phys. Rev. B* **2018**, *98*, No. 035425.
- (49) Kim, Y.; et al. Charge Inversion and Topological Phase Transition at a Twist Angle Induced van Hove Singularity of Bilayer Graphene. *Nano Lett.* **2016**, *16*, 5053–5059.
- (50) Berdyugin, A. I.; Tsim, B.; Kumaravadivel, P.; Xu, S. G.; Ceferino, A.; Knothe, A.; Kumar, R. K.; Taniguchi, T.; Watanabe, K.; Geim, A. K.; Grigorieva, I. V.; Fal'ko, V. I. Minibands in twisted bilayer graphene probed by magnetic focusing. *Sci. Adv.* **2020**, *6*, No. eaay7838.
- (51) Kim, Y.; Moon, P.; Watanabe, K.; Taniguchi, T.; Smet, J. H. Odd Integer Quantum Hall States with Interlayer Coherence in Twisted Bilayer Graphene. *Nano Lett.* **2021**, *21*, 4249–4254.
- (52) Yankowitz, M.; et al. Tuning superconductivity in twisted bilayer graphene. *Science* **2019**, *363*, 1059–1064.
- (53) Piccinini, G.; Miseikis, V.; Watanabe, K.; Taniguchi, T.; Coletti, C.; Pezzini, S. Parallel transport and layer-resolved thermodynamic measurements in twisted bilayer graphene. *Phys. Rev. B* **2021**, *104*, L241410.
- (54) Novelli, P.; Torre, I.; Koppens, F. H. L.; Taddei, F.; Polini, M. Optical and plasmonic properties of twisted bilayer graphene: Impact of interlayer tunneling asymmetry and ground-state charge inhomogeneity. *Phys. Rev. B* **2020**, *102*, 125403.
- (55) Hesp, N. C. H.; et al. Observation of interband collective excitations in twisted bilayer graphene. *Nat. Phys.* **2021**, *17*, 1162–1168.
- (56) Giuliani, G. F.; Vignale, G. *Quantum Theory of the Electron Liquid*; Cambridge Univ. Press: Cambridge, England, 2005.
- (57) Berthod, C.; Zhang, H.; Morpurgo, A. F.; Giamarchi, T. Theory of cross quantum capacitance. *Phys. Rev. Res.* **2021**, *3*, No. 043036.
- (58) Slizovskiy, S.; et al. Out-of-Plane Dielectric Susceptibility of Graphene in Twistrionic and Bernal Bilayers. *Nano Lett.* **2021**, *21*, 6678–6683.
- (59) Hejazi, K.; Liu, C.; Balents, L. Landau levels in twisted bilayer graphene and semiclassical orbits. *Phys. Rev. B* **2019**, *100*, No. 035115.
- (60) Krishna Kumar, R.; Chen, X.; Auton, G. H.; Mishchenko, A.; Bandurin, D. A.; Morozov, S. V.; Cao, Y.; Khestanova, E.; Ben Shalom, M.; Kretinin, A. V.; Novoselov, K. S.; Eaves, L.; Grigorieva, I. V.; Ponomarenko, L. A.; Fal'ko, V. I.; Geim, A. K. High-temperature quantum oscillations caused by recurring Bloch states in graphene superlattices. *Science* **2017**, *357*, 181–184.
- (61) Kumar, R. K.; Mishchenko, A.; Chen, X.; Pezzini, S.; Auton, G. H.; Ponomarenko, L. A.; Zeitzer, U.; Eaves, L.; Fal'ko, V. I.; Geim, A. K. High-order fractal states in graphene superlattices. *Proc. Natl. Acad. Sci. U.S.A.* **2018**, *115*, 5135–5139.
- (62) Barrier, J.; Kumaravadivel, P.; Krishna Kumar, R.; Ponomarenko, L. A.; Xin, N.; Holwill, M.; Mullan, C.; Kim, M.; Gorbachev, R. V.; Thompson, M. D.; Prance, J. R.; Taniguchi, T.; Watanabe, K.; Grigorieva, I. V.; Novoselov, K. S.; Mishchenko, A.; Fal'ko, V. I.; Geim, A. K.; Berdyugin, A. I. Long-range ballistic transport of Brown-Zak fermions in graphene superlattices. *Nat. Commun.* **2020**, *11*, 5756.
- (63) Ponomarenko, L. A.; et al. Cloning of Dirac fermions in graphene superlattices. *Nature* **2013**, *497*, 594–597.

- (64) Dean, C. R.; et al. Hofstadter's butterfly and the fractal quantum Hall effect in moiré superlattices. *Nature* **2013**, *497*, 598–602.
- (65) Hunt, B.; et al. Massive Dirac Fermions and Hofstadter Butterfly in a van der Waals Heterostructure. *Science* **2013**, *340*, 1427–1430.
- (66) Phinney, I. Y.; et al. Strong interminivalley scattering in twisted bilayer graphene revealed by high-temperature magneto-oscillations. *Phys. Rev. Lett.* **2021**, *127*, No. 056802.
- (67) Yin, J.; Wang, H.; Peng, H.; Tan, Z.; Liao, L.; Lin, L.; Sun, X.; Koh, A. L.; Chen, Y.; Peng, H.; Liu, Z. Selectively enhanced photocurrent generation in twisted bilayer graphene with van Hove singularity. *Nat. Commun.* **2016**, *7*, 10699.
- (68) Sunku, S. S.; et al. Photonic crystals for nano-light in moiré graphene superlattices. *Science* **2018**, *362*, 1153–1156.
- (69) Tomadin, A.; Guinea, F.; Polini, M. Generation and morphing of plasmons in graphene superlattices. *Phys. Rev. B* **2014**, *90*, 161406.
- (70) Zhang, Y.; et al. Ascendance of Superconductivity in Magic-Angle Graphene Multilayers. *arXiv* 2112.09270, 2021, accessed 2022-06-27.
- (71) Park, J. M.; et al. Magic-Angle Multilayer Graphene: A Robust Family of Moiré Superconductors. *arXiv* 2112.10760, 2021, accessed 2022-06-27.

□ Recommended by ACS

Observation of Robust and Long-Ranged Superperiodicity of Electronic Density Induced by Intervalley Scattering in Graphene/Transition Metal Dichalcogenide Heterostructures

Mo-Han Zhang, Lin He, et al.

APRIL 03, 2023

NANO LETTERS

READ ↗

Chiral Decomposition of Twisted Graphene Multilayers with Arbitrary Stacking

ShengNan Zhang, Oleg V. Yazyev, et al.

MARCH 20, 2023

NANO LETTERS

READ ↗

Modulation of Remote Epitaxial Heterointerface by Graphene-Assisted Attenuative Charge Transfer

Yuning Wang, Ke Xu, et al.

FEBRUARY 06, 2023

ACS NANO

READ ↗

Remote Epitaxy and Exfoliation of GaN via Graphene

Xu Han, Lai Wang, et al.

OCTOBER 25, 2022

ACS APPLIED ELECTRONIC MATERIALS

READ ↗

Get More Suggestions >